

MAGNETIC PHASE DIAGRAM OF Dy₃Co SINGLE CRYSTAL*

P. SVOBODA

Department of Electronic Structures, Charles University
121 16 Prague 2, The Czech Republic

H. NAKOTTE, A.M. ALSMADI

New Mexico State University, Las Cruces, NM 88003-8001, USA

AND M. DOERR

IAPD, TU-Dresden, 01062 Dresden, Germany

(Received July 10, 2002)

A detailed study of Dy₃Co single crystal in moderate magnetic fields is presented. It forms the orthorhombic structure (Fe₃C-type, space group Pnma) and orders antiferromagnetically (AF) at $T_N = 72$ K. At least three additional AF phases exist below T_N with corresponding transition temperatures $T_1 = 43$ K, $T_2 = 33$ K and $T_3 = 24$ K, respectively. Step-like metamagnetic transitions were observed along all three crystallographic axes. The respective complex magnetic phase diagrams are presented.

PACS numbers: 75.30.-m, 75.25.+z, 75.30.Kz

1. Introduction

The intermetallic compound Dy₃Co crystallizes in the orthorhombic structure of the Fe₃C-type [1, 2] where Dy atoms occupy two sites 4c and 8d, respectively, and Co occupies another 4c position. As no magnetic moment was found on Co, the magnetic order is a result of an indirect interaction of Dy moments mediated via conduction electrons [3, 4]. The antiferromagnetic (AF) ordering was reported at temperatures below 45 K. Observed metamagnetic behavior accompanied by large magnetoresistance effect along all

* Presented at the International Conference on Strongly Correlated Electron Systems, (SCES 02), Cracow, Poland, July 10-13, 2002.

three principal crystallographic axes suggests complex AF structure and rich magnetic phase diagram [4].

Here we report on the new bulk and microscopic results of the high-quality single crystal of Dy_3Co . An updated magnetic phase diagram is presented.

2. Experimental results and discussion

The single crystal of Dy_3Co was prepared by remelting the polycrystalline sample in the high-gradient resistance furnace (for details see [4]). A single crystalline grain of about $1 \times 1 \times 1 \text{ mm}^3$ was cut out of the ingot. The high quality of the crystal was confirmed by neutron diffraction.

The temperature dependence of ac-susceptibility was measured on this crystal in several magnetic fields parallel to the crystallographic axes using the $f = 512 \text{ Hz}$ driving field with $H = 2 \text{ Oe}$ amplitude. A pronounced anomaly was found at $T = 72 \text{ K}$ (see Fig. 1) in zero field suggesting that the AF magnetic ordering occurs already at this temperature, higher than reported in [4]. Additional anomalies exist on the ac-susceptibility, the most pronounced ones at $T = 43$ and 28 K .

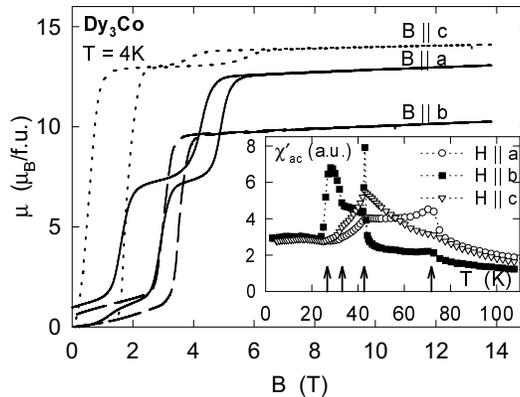


Fig. 1. Magnetization curves along principal crystallographic axes in the ground-state phase. The inset shows the temperature dependencies of ac-susceptibility, the arrows mark the transitions obtained from the neutron diffraction.

Magnetization curves measured both on SQUID and VSM in fields up to 14 T along all three axes exhibit the step-like metamagnetic behavior (with pronounced hysteresis phenomena at temperatures below $\sim 20 \text{ K}$). In fields above 6 T the curves saturate, yielding the spontaneous magnetic moment $\mu = 12.23, 9.40$ and $13.64 \mu_B/f.u.$ along a, b and c axis, respectively. With the increasing temperature the sharp transitions become smeared-out, but traces of metamagnetic behavior can be followed up to $T = 72 \text{ K}$.

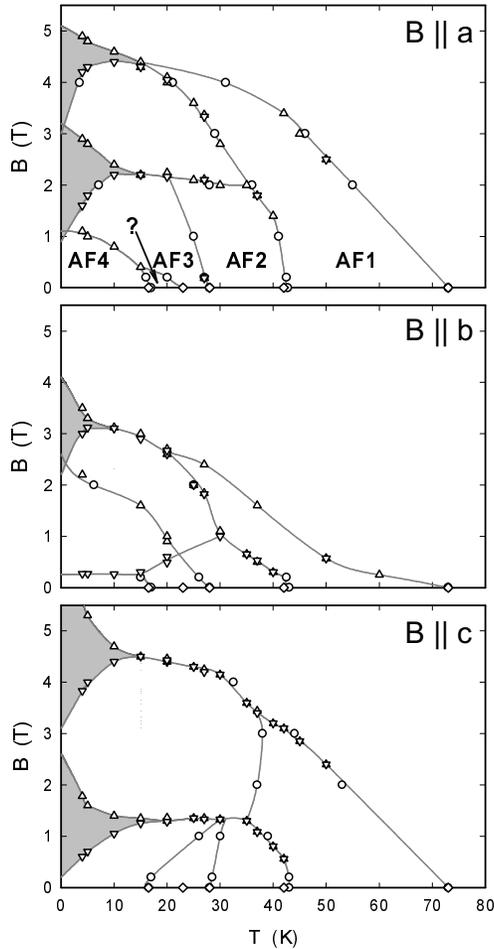


Fig. 2. Magnetic phase diagrams of Dy_3Co in fields parallel to the principal crystallographic directions based on the magnetization (Δ , ∇), ac-susceptibility (\circ) and neutron diffraction (\diamond) data. The grey areas correspond to the hysteresis phenomena.

This result had motivated the detailed neutron diffraction studies performed in BENSIC, HMI, using E4 and E5 diffractometers with incident wavelength $\lambda = 2.4 \text{ \AA}$. The temperature dependence of some magnetic intensities unambiguously proves, that the Néel temperature is indeed $T_N = 72 \text{ K}$.

The ground-state magnetic structure is characterized by two propagation vectors $\mathbf{k}_1 = (0 \ 0 \ 0)$ and $\mathbf{k}_2 = (1/2 \ 0 \ 1/2)$ [4,5]. While the \mathbf{k}_2 propagation disappears at $T = 28 \text{ K}$, the \mathbf{k}_1 propagation remains till T_N . Contrary to the frequent situation, where an incommensurate magnetic phase appears just below T_N , no additional propagation was found in the ordered state.

All these data enabled us to construct the magnetic phase diagram (Fig. 2), but the details of the individual phases has still to be completed. As the saturated magnetization values are far from the maximum theoretical value based on the free Dy^{3+} ion ($30 \mu_{\text{B}}/\text{f.u.}$), additional metamagnetic transitions can be expected in higher magnetic fields. Moreover, the \mathbf{k}_1 propagation was observed in the magnetic field $B = 6$ T, indicating that this phase is not yet the field-induced ferromagnetic one.

This work is a part of the ME CR research program MSM113200002. Part of it was also supported by the GACR 106/02/0940, NSF grant No. DMR-0094241 and the Sonderforschungsbereich program 463. The neutron diffraction study has been supported by the EU (IHP-ARI contract HPRI-CT-1999-00020).

REFERENCES

- [1] K.H.J. Buschow, A.S. van der Goot, *J. Less-Common Met.* **18**, 309 (1969).
- [2] O.A.W. Strydom, L. Alberts, *J. Less-Common Met.* **22**, 511 (1970).
- [3] D. Gignoux *et al.*, *Solid State Commun.* **8**, 391 (1970).
- [4] N.V. Baranov *et al.*, *J. Alloys and Comp.* **226**, 70 (1995).
- [5] A.E. Teplykh *et al.*, *Mat. Sci. Forum* **321-324**, 653 (2000).