

HEAVY QUASIPARTICLES AND PSEUDOGAP FORMATION IN YbAl_3 : OPTICAL CONDUCTIVITY STUDY*

H. OKAMURA

Department of Physics, Kobe University, Kobe 657-8501, Japan

T. EBIHARA

Department of Physics, Shizuoka University, Shizuoka 422-8529, Japan

T. NANBA

Graduate School of Science and Technology
Kobe University, Kobe 657-8501, Japan

(Received July 10, 2002)

We have measured the optical conductivity $\sigma(\omega)$ of the mixed-valent compound YbAl_3 . $\sigma(\omega)$ exhibits a mid-infrared peak centered at 0.15–0.2 eV, which becomes more pronounced with decreasing temperature (T). In addition, a strong depletion of the spectral weight, *i.e.*, a pseudogap formation, is observed in $\sigma(\omega)$ below ~ 0.1 eV. A comparison of $\sigma(\omega)$ with the dc conductivity indicates the existence of an extremely narrow Drude peak at very low energy. Energy-dependent effective mass and scattering rate of the carriers are evaluated from the optical data, which indicates the formation of a heavy-mass Fermi liquid state within ~ 40 meV from the Fermi level. These observations are discussed in terms of the hybridization of a conduction band and a narrow $4f$ band.

PACS numbers: 71.27.+a, 78.20.-e

YbAl_3 is a valence-fluctuating (VF) compound which is gaining increasing interest recently [1–3]. At low temperature (T), de Haas–van Alphen oscillations of YbAl_3 were clearly observed, indicating the formation of heavy mass Fermi liquid with effective masses of 14–24 m_0 [2]. The magnetic susceptibility (χ) shows a local moment (Curie–Weiss) behavior at high T and

* Presented at the International Conference on Strongly Correlated Electron Systems, (SCES 02), Cracow, Poland, July 10–13, 2002.

a broad maximum at $T_{\max} \sim 120$ K, which is typical of VF compounds with a Kondo temperature of ~ 500 K. Typically, properties such as χ and the electronic specific heat (C_e) for such VF compounds show T dependences that are very similar to predictions of the Anderson impurity model (AIM). However, recent work on high quality single crystalline YbAl_3 has shown that $\chi(T)$ and $C_e(T)$ below ~ 40 K deviate from the predictions of AIM. In the same T range, the resistivity shows a T^2 dependence, *i.e.*, a Fermi liquid property. These observations suggest that effects of the Yb lattice may be responsible for the deviation from AIM [3].

In this work, we use optical spectroscopy to probe the interesting electronic structures of YbAl_3 near the Fermi level (E_F). The YbAl_3 and LuAl_3 samples used in this work were high-quality single crystals grown with a self-flux method [1]. The optical reflectivity $R(\omega)$ was measured in the range 20 meV–30 eV under a near-normal incidence. Optical conductivity $\sigma(\omega)$ was obtained from a measured $R(\omega)$ using Kramers–Kronig relations [4]. For low-energy extrapolation, a Hagen–Rubens formula was used [4]. More details of the optical experiments can be found elsewhere [5].

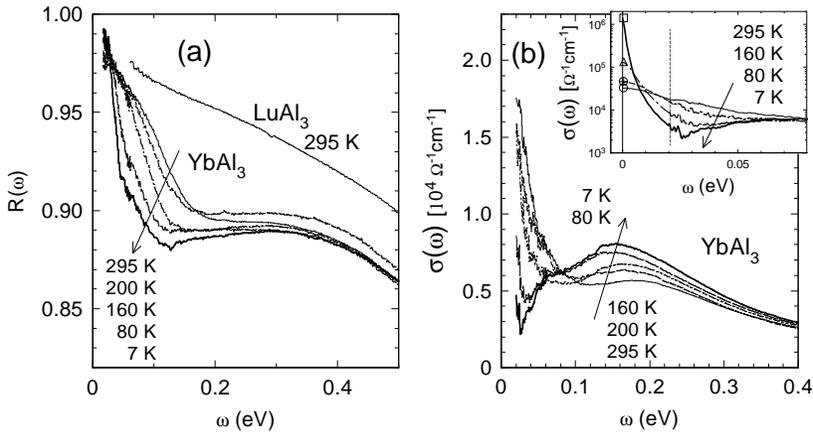


Fig. 1. (a) Infrared optical reflectivity $R(\omega)$ of YbAl_3 and LuAl_3 . (b) Optical conductivity [$\sigma(\omega)$] of YbAl_3 . The inset compares low-energy $\sigma(\omega)$ with the corresponding σ_{dc} , indicated by the symbols on the vertical axis (note the logarithmic scale). The $\sigma(\omega)$ curves below 0.02 eV are extrapolations.

Figure 1(a) shows $R(\omega)$ of YbAl_3 at temperatures $7 \text{ K} \leq T \leq 295 \text{ K}$, and that of non-magnetic LuAl_3 at 295 K. YbAl_3 has a broad dip in $R(\omega)$, which is strongly T -dependent and becomes more pronounced with decreasing T . In contrast, LuAl_3 has no such feature, indicating that the dip for YbAl_3 results from Yb $4f$ -related states near E_F . Figure 1(b) shows $\sigma(\omega)$ of YbAl_3 . It is seen that the broad dip in $R(\omega)$ gives rise to a strong mid-IR peak in $\sigma(\omega)$, which grows with decreasing T . At the same time, the spectral

weight below the mid-IR peak energy is gradually depleted with decreasing T . This spectral depletion in $\sigma(\omega)$, *i.e.*, a pseudogap formation, shows that the density of states in the region 10-50 meV away from E_F becomes small at low T . This may appear striking since YbAl₃ is a good metal, with a dc conductivity σ_{dc} exceeding $10^6 \Omega^{-1}\text{cm}^{-1}$ at 7 K [1]. σ_{dc} and $\sigma(\omega)$ are compared to each other in the inset of Fig. 1(b), where σ_{dc} are indicated by the symbols on the vertical axis. It is immediately apparent that a narrow Drude peak, *i.e.*, a very sharp rise in $\sigma(\omega)$, should exist in the low-energy region below the measurement range of this work. A similar spectral feature was first reported for mixed-valent CePd₃ [6], and later for many other f -electron compounds [7]. The narrow Drude peaks in these works have been understood in terms of the electrodynamical response of a heavy-mass Fermi liquid, *i.e.*, a “heavy fermion plasma” [8]. Namely, the formation of a spatially coherent heavy fermion state leads to a large effective mass and a reduced scattering rate of the carriers. Since the scattering rate is directly related to the width of a Drude peak in $\sigma(\omega)$, it becomes extremely narrow, often observed in the microwave region [7].

In addition to the narrow Drude peak, the present data show two key features in $\sigma(\omega)$, namely the mid-IR peak and the pseudogap below ~ 0.1 eV. Again, similar features have been observed for many heavy fermion and mixed valent compounds. A generally accepted mechanism leading to such spectral features is a hybridization of wide conduction (c) band and a narrow f band. This c - f hybridization leads to the formation of a small energy gap, and the optical excitation of quasiparticles across this gap leads to a mid-IR peak in $\sigma(\omega)$. Heavy fermions arise when E_F is located slightly above or below the gap. It is noteworthy that the spectral variation between 7 K and 40 K (not shown) was much smaller than that between 40 K and 80 K. This may be regarded as evidence that the development of c - f hybridization state is complete below 40 K, which is consistent with the resistivity data showing a T^2 (Fermi liquid) dependence below 40 K.

In order to obtain more information about the electronic structures near E_F of YbAl₃, we apply the so-called “generalized Drude” analysis [7] to the present data. In this model, the energy-dependent scattering rate $1/\tau(\omega)$ and optical effective mass $m^*(\omega)$ of the quasiparticles can be evaluated from the optical spectra. Figure 2 shows the results. Below 80 K, $1/\tau(\omega)$ is strongly suppressed at energies below ~ 40 meV, where it shows approximately a ω^2 dependence. This strongly suggests the formation of a coherent Fermi liquid state. $m^*(\omega)$ below ~ 40 meV becomes large with decreasing T , reaching about 25 times the bare band mass at 7 K. The observed behaviors of $1/\tau(\omega)$ and $m^*(\omega)$ indicate that a Fermi liquid state with a heavy mass is formed within ~ 40 meV from E_F . The mass enhancement factor of 25 is close to the cyclotron masses of 14-24 m_0 deduced from the de Haas-

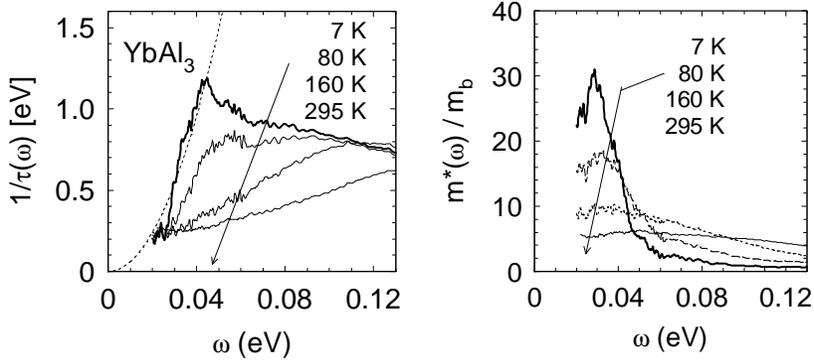


Fig. 2. Energy-dependent scattering rate $1/\tau(\omega)$ and effective mass $m^*(\omega)$ normalized by optical band bass m_b for YbAl_3 , obtained using the generalized Drude model. The dotted curve in the left graph is guide to the eye, showing a ω^2 dependence.

van Alphen data [2]. The observed T dependences of $1/\tau(\omega)$ and $m^*(\omega)$ are quite similar to those previously reported for CePd_3 [6], where $\sigma(\omega)$ was measured to much lower energy (0.5 meV) than in the present work. Hence, although our measurement range is not sufficient to directly observe the narrow Drude peak in $\sigma(\omega)$, the present data appear to have captured important features of the heavy fermion dynamics in YbAl_3 . Measurements in lower-energy region are in progress, to study the heavy fermion dynamics more quantitatively.

We thank J. Lawrence for useful comments on this work. This work is funded by Grant-in-Aid from MEXT of Japan. T.E. is financially supported by Yukawa Foundation and Corning Japan.

REFERENCES

- [1] T. Ebihara *et al.*, *Physica* **B281&282**, 754 (2000).
- [2] T. Ebihara *et al.*, *J. Phys. Soc. Jpn.* **69**, 895 (2000).
- [3] A.L. Cornelius *et al.*, *Phys. Rev. Lett.* **88**, 117201 (2002).
- [4] F. Wooten, *Optical Properties of Solids*, Academic Press, New York 1972.
- [5] H. Okamura *et al.*, *Phys. Rev.* **B62**, R13265 (2000).
- [6] B.C. Webb, A.J. Sievers, T. Mihalisin, *Phys. Rev. Lett.* **57**, 1951 (1986).
- [7] L. Degiorgi, *Rev. Mod. Phys.* **72**, 687 (1999), and references therein.
- [8] A.J. Millis, P.A. Lee, *Phys. Rev.* **B35**, 3394 (1987).