

FERMI SURFACE OF ANTIFERROMAGNET UPtGa₅ IN RELATIVISTIC SPIN-POLARIZED BAND THEORY*

HIROSHI YAMAGAMI

Department of Physics, Faculty of Science, Kyoto Sangyo University
Kyoto, 603-8555, Japan

(Received July 10, 2002)

A first-principle study of Fermi surface and magnetism for antiferromagnet UPtGa₅ is done by all-electron band calculations using fully-relativistic spin-polarized LAPW method in a local spin-density approximation. The Fermi surfaces, mainly having cylinder-like shapes with open structure along the [001] direction, explain well the angular-dependence of de Haas-van Alphen frequencies. In a picture of 5*f*-band antiferromagnet, the local magnetic moment at U site is in good agreement with the observed moment.

PACS numbers: 71.18.+y, 71.20.-b

1. Introduction

UPtGa₅ shows an antiferromagnetic ordering below 25K, and the local magnetic moments at the U site are arranged with the wave vector $Q = (0, 0, 1/2)$ and the easy axis along the [001] direction [1]. The crystal structure belongs to HoCoGa₅-type tetragonal structure with a symmetry of P4/*mmm* [2]. Recent de Haas-van Alphen (dHvA) measurements clarify that the Fermi surfaces of UPtGa₅ are basically cylindrical along the [001] direction [3, 4]. The topology of Fermi surface is found to be different from that of UNiGa₅ [5] with the same crystal structure, but a different magnetic structure of $Q = (1/2, 1/2, 1/2)$ [1]. The angular dependence of dHvA frequencies in UNiGa₅ has been explained from the band theory together with magnetic moments [6].

In the paper a first-principle study of Fermi surface and magnetism for antiferromagnet UPtGa₅ is performed by all-electron band calculations using a fully-relativistic spin-polarized LAPW method [7] within exchange-corre-

* Presented at the International Conference on Strongly Correlated Electron Systems, (SCES 02), Cracow, Poland, July 10-13, 2002.

lation potentials in a local spin-density approximation [8]. Accordingly we obtain a theoretical evidence to show that the antiferromagnetic structure directly controls the topology of Fermi surfaces for UNiGa₅ and UPtGa₅.

2. Calculated results and discussion

In the self-consistent calculations the $5f$, $6p$, $6d$ and $7s$ electrons in the U site, the $5d$ and $7s$ in the Pt site and the $3d$, $4s$ and $4p$ in the Ga site are treated as valence electrons. The densities and potentials are constructed in the muffin-tin approximation. The magnetic moments at the U site are oriented antiferromagnetically along the $[001]$ direction using a local spin-rotation technique [7] and the magnetic directions around the Pt atoms are set along the $[001]$ direction so as to hold a magnetic symmetry. The lattice constants are set to experimental values of $a = 4.3426 \text{ \AA}$ and $c = 6.8120 \text{ \AA}$.

Fig. 1 show total and partial density of state (DOS) for antiferromagnet UPtGa₅, where the dashed lines presents the Fermi energy (E_F). The Ga(1) and Ga(2) denote two different positions of the Ga atom in UPtGa₅: those are Ga(1)=(1/2,1/2,0) and Ga(2)=(0,1/2, z) with $z = 0.295$ in the unit cell. The $5f$ bands around E_F are hybridized mainly with the U- $6d$ bands and the Ga(2)- $4p$ bands. The theoretical electronic specific heat coefficient γ_b is estimated as 22.52 mJ/K² mole from the total DOS at E_F . The experimental

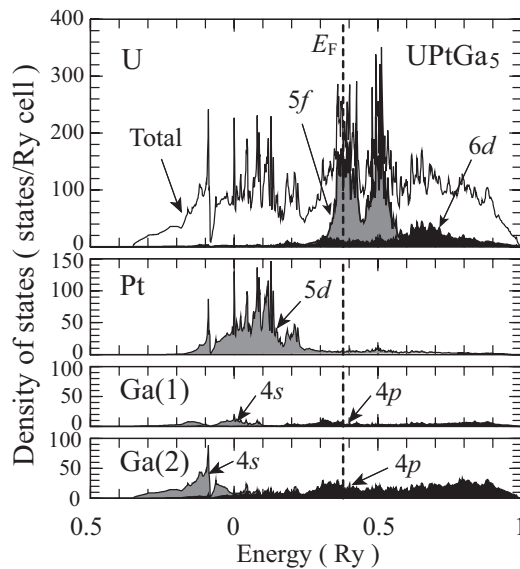


Fig. 1. Total and partial density of states partitioned into the U, Pt, Ga(1) and Ga(2) sites.

value is $\gamma_{\text{exp}}=57 \text{ mJ/K}^2 \text{ mole}$ [3]. The enhancement factor ($\lambda = \gamma_{\text{exp}}/\gamma_{\text{b}}-1$) is thus found to be of a small value of 1.53.

The Fermi surfaces are composed of $5f$ -rich bands with 30 to 34 band-indices, which are adopted to a number counted up from the bottom of the valence electron. In Fig. 2 the shape of the Fermi surfaces is shown within a tetragonal Brillouin zone in the antiferromagnetic state. All the Fermi surfaces except the band 34-electron surface have cylinder-like shapes with open structure along the $[001]$ direction.

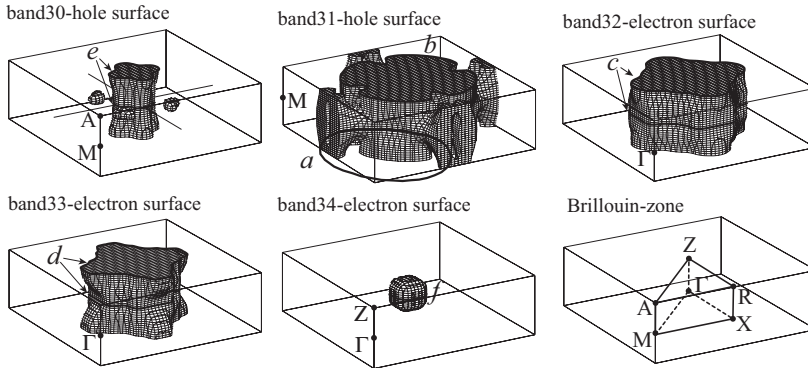


Fig. 2. Fermi surface of antiferromagnet UPtGa₅. The band30- and band31-hole surfaces are drawn at the center of the Γ point in the Brillouin zone and the band32- to band34-electron surfaces are centered as the M point.

The extremal cross-sectional area (ECSA) of the Fermi surface is proportional to the dHvA frequency. Fig. 3 shows a quantitative comparison between the theoretical (solid lines) and the observed results (circles) [4] in the angular dependence of the dHvA frequencies. The theoretical branch a , d and e in Fig. 3 obviously correspond to the experimental branch ε , α_1 (α_2) and γ , respectively. The orbits of the theoretical branches with respect to the $[001]$ field direction are presented in Fig. 2. The branch α_3 naturally originates from the branch c or/and a part of the branch b_1 and b_2 , each of which is the branch b (Fig. 2) in the case that the center of ECSA is set at the Z and Γ point. The remaining branch f is not observed here. Additionally the cyclotron masses at the $[001]$ field angle for branch a , b , c , d , e and f are given as 3.63, 4.81, 3.43, 3.19 and 3.04, 1.65 and 1.56 in units of electron mass m_0 , though it is not discussed here for lack of space.

For the magnetic properties the spin- and orbital-moment at the U site are calculated as $-2.55\mu_{\text{B}}$ and $2.84\mu_{\text{B}}$, respectively. The local magnetic moment is thus $0.29\mu_{\text{B}}$. It is in good agreement with the experimental value of $0.24\mu_{\text{B}}$ [1].

It is thus suggested that UPtGa₅ should be a $5f$ -band antiferromagnet in a viewpoint of the fermiology and magnetic moment.

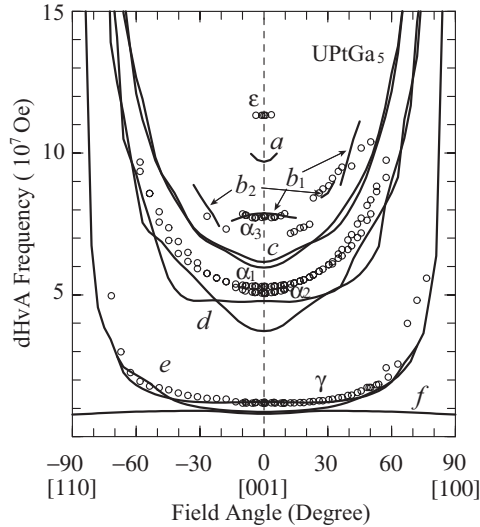


Fig. 3. Comparison between theoretical and experimental results of de Haas–van Alphen frequencies in UPtGa_5 . The theoretical results are indicated by solid lines and the experimental results are denoted by circles [4].

I gratefully acknowledge helpful discussions with Prof. Y. Ōnuki and Dr. Y. Inada on the dHvA effect and Fermi surface in UPtGa_5 .

REFERENCES

- [1] Y. Tokiwa, Y. Haga, N. Metoki, Y. Ishii, Y. Ōnuki, *J. Phys. Soc. Jpn.* **71**, 725 (2002).
- [2] Yu.N. Grin, P. Pogl, K. Hiebl, *J. Less-Common Met.* **121**, 497 (1986).
- [3] Y. Tokiwa, S. Ikeda, Y. Haga, T. Okubo, K. Sugiyama, A. Nakamura, Y. Ōnuki, *J. Phys. Soc. Jpn.* **71**, 845 (2002).
- [4] S. Ikeda, Y. Tokiwa, T. Ōkubo, M. Yamada, D. Matsuda, Y. Inada, R. Settai, E. Yamamoto, Y. Haga, Y. Ōnuki, to be submitted to LT23 proceedings.
- [5] Y. Tokiwa, Y. Haga, E. Yamamoto, D. Aoki, N. Watanabe, R. Settai, T. Inoue, K. Kindo, H. Harima, Y. Ōnuki, *J. Phys. Soc. Jpn.* **70**, 1744 (2001).
- [6] H. Yamagami, *Physica B* **312**, 297 (2002).
- [7] H. Yamagami, *Phys. Rev.* **B61**, 6246 (2000).
- [8] U. von Barth, L. Hedin, *J. Phys.* **C5**, 1629 (1972).