

# ULTRASONIC ATTENUATION AND ELASTICITY IN URu<sub>2</sub>Si<sub>2</sub>\*

B. WOLF, S. ZHERLITSYN, M. LANG, B. LÜTHI

Physikalisches Institut, Universität Frankfurt, D-60054 Frankfurt, Germany

AND A.A. MENOVSKY

Kamerlingh Onnes Laboratory, Leiden University, Leiden, The Netherlands

*(Received July 10, 2002)*

We present ultrasonic attenuation and elastic constant results on the heavy-fermion state of URu<sub>2</sub>Si<sub>2</sub> both as a function of temperature and magnetic fields up to 50 T. We find distinct anomalies as a function of field and temperature for the longitudinal modes  $c_{11}$  and  $c_{33}$ . We construct a  $B$ - $T$  phase diagram including  $T_N(B)$ , the so-called metamagnetic transition and the spin-flop transition into the paramagnetic phase.

PACS numbers: 75.30.Mb, 74.25.Ld, 43.35.+d

## 1. Introduction

Most heavy-fermion compounds, in addition to strong antiferromagnetic fluctuations, order magnetically at low temperatures. In URu<sub>2</sub>Si<sub>2</sub> the phase transition at  $T_N = 17.4$  K has been attributed to such an antiferromagnetic order. In addition, the system becomes superconducting below  $T_c = 1.2$  K. The great mystery in URu<sub>2</sub>Si<sub>2</sub> is the measured moment of  $0.03 \mu_B$  in the ordered phase, which is too small to account for the large specific heat anomaly at  $T_N$ . Many different experimental facts have pointed to a so far unidentified type of phase transition, which we label therefore a pseudomagnetic transition. For a review on the properties and physics of this pseudomagnetic transition see Ref. [1].

---

\* Presented at the International Conference on Strongly Correlated Electron Systems, (SCES 02), Cracow, Poland, July 10–13, 2002.

## 2. Experiments

Acoustic experiments in URu<sub>2</sub>Si<sub>2</sub> concentrated in the past on an investigation of the superconducting transition at  $T_c$  [2] and the overall temperature dependence of the elastic constants [2–4]. It was found that the longitudinal elastic constants show anisotropic behaviour in the normal and superconducting state. The temperature dependence could be well described with the so-called Grüneisen parameter coupling, especially for the longitudinal  $c_{11}$  mode. This coupling arises from the volume dependence of the narrow quasi-particle band of the heavy-fermion systems. For anisotropic systems it is useful to introduce the uniaxial Grüneisen parameters  $\Omega_a$  and  $\Omega_c$ , which are related to the uniaxial pressure dependences of the characteristic temperature.

The elastic anomalies around the pseudomagnetic transition at 17.4 K are anomalous and quite different in comparison to typical uniaxial antiferromagnets [5] and have been attributed to a spin-nematic strain coupling, *i.e.* a strain coupling to itinerant quadrupoles of the quasiparticles. Fig. 1(a) exhibits  $\Delta c_{ii}/c_{ii}(0)$  for the longitudinal modes  $c_{11}$ ,  $c_{33}$  and the transverse modes  $c_{44}$ ,  $c_{66}$ . The anomalies are rather weak and no precursor effect is observed for  $T > T_N$ . This behaviour has to be contrasted with results for large moment uniaxial antiferromagnets like UPd<sub>2</sub>Al<sub>3</sub> [5] or MnF<sub>2</sub> [6] where pronounced minima in the elastic modes are found. In Fig. 1(b) we show ultrasonic attenuation results at frequencies  $\omega$  of 400–600 MHz. Again the attenuation anomalies are quite different from those observed in ordinary antiferromagnets, *e.g.* MnF<sub>2</sub> and RbMnF<sub>3</sub> [7]. While the height of the maximum follows roughly a  $\omega^2$  dependence there is no clear singularity at  $T_N$  but instead a broad maximum. Further on,  $\alpha(T)$  drops rapidly below  $T_N$  different from a power-law dependence but reminiscent of the behaviour found in a BCS superconductor. Accordingly, the ultrasonic attenuation can be described with a mean-field like expression using a gap value comparable to those observed in specific heat or the resistivity measurements. This result indicates that the elastic waves couple in the first place to a (spin)-density wave forming on a part of the Fermi surface below  $T_N$ . Accordingly, the elastic constant changes, shown in Fig. 1(a), may reflect changes in the deformation potential coupling constant upon cooling through  $T_N$ .

In Fig. 2(a) we show elastic constant and attenuation data for the longitudinal  $c_{11}$  mode as a function of magnetic field. The attenuation data of the  $c_{11}$  mode in Fig. 2(a) help to pinpoint the anomalies already seen in the sound velocity measurements published before [9]. The  $\alpha(B)$  data appear as pronounced spikes for the transitions at 34.2 T, 36.1 T and 38.7 T (at 4.2 K). The spin-flop transition at 38.7 T exhibits only a smaller and broader attenuation anomaly, similar to those observed before in uniaxial an-

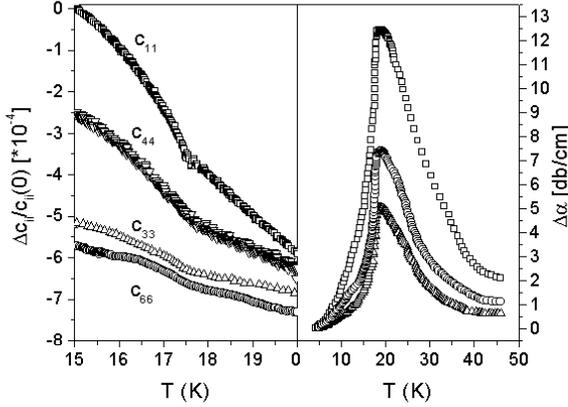


Fig. 1. (a) Relative elastic constant changes for the modes  $c_{11}$ ,  $c_{33}$ ,  $c_{44}$  and  $c_{66}$  in the vicinity of  $T_N$ . (b) Attenuation near  $T_N$  for sound waves of 400 MHz (diamonds), 500 MHz (circles) and 600 MHz (squares).

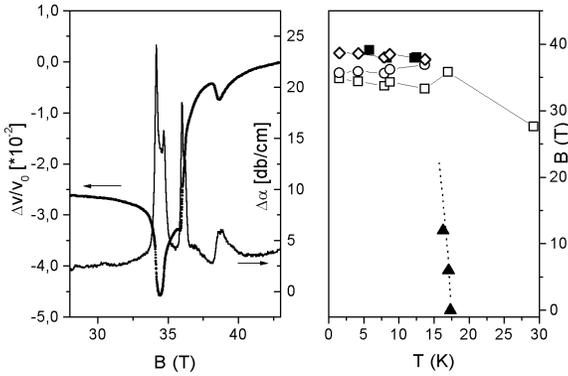


Fig. 2. (a) Ultrasonic attenuation at 4.2 K for the  $c_{11}$  mode at 46.6 MHz. Included is also the relative velocity change at the same temperature. (b)  $B$ - $T$  phase diagram constructed from elastic anomalies. Pulse-field experiments: filled squares  $c_{33}(B)$  mode; open diamonds, open circles, open squares  $c_{11}(B)$ ; filled triangles from  $c_{11}(T)$  in constant field.

tiferromagnets [10]. Especially at the metamagnetic transition at 34.2 T the ultrasonic attenuation anomaly is strongly enhanced and the elastic constant exhibits a pronounced minimum. This behaviour is similar to the metamagnetic transitions in other heavy-fermion systems like  $CeRu_2Si_2$  or  $UPt_3$  [11]. At the moment there is no explanation for the attenuation peak at 36.1 T, which is also clearly seen in the magnetic susceptibility [8].

Finally we can construct a  $B$ - $T$  phase diagram as shown in Fig. 2(b) from the data of Figs. 1(a), (b), 2(a), and the data of Ref. [9]. The open symbols are determined from the  $c_{11}$  anomalies where the open squares indicate the metamagnetic transition. The open diamonds and the filled squares mark the phase boundary between the antiferromagnetic and the paramagnetic state. Apparently  $T_N(B)$  does not connect to the metamagnetic transition, which can be followed at least up to 30 K in the  $c_{11}$  mode.

### 3. Summary

In summary, the high-field data of URu<sub>2</sub>Si<sub>2</sub> can be explained for increasing field with a change from itinerant to a more localized picture of an uniaxial magnet. The metamagnetic transition at 34.2 T is pronounced for the  $c_{11}$  mode with a large  $\Omega_a$  and absent for  $c_{33}$  with a small  $\Omega_c$  in agreement with the temperature-dependent measurements. For higher fields, where the heavy-fermion state changes to a localized spin state both modes give pronounced effects at the spin flop state. On the other hand the zero-field data for the elastic constant and the attenuation in the vicinity of  $T_N$  are so far unexplained although they show a behaviour typical for a coupling between the strain and a spin density wave. Whether this coupling is related to the hidden order parameter [12] is not clear yet.

### REFERENCES

- [1] W.B.L. Buyers, *Physica B* **223–224**, 9 (1996).
- [2] B. Wolf *et al.*, *J. Low Temp. Phys.* **94**, 307 (1994).
- [3] B. Lüthi *et al.*, *J. Low Temp. Phys.* **95**, 257 (1994).
- [4] K. Kuwahara *et al.*, *J. Phys. Soc. Jpn.* **66**, 3251 (1997).
- [5] B. Lüthi *et al.*, *Phys. Lett.* **A175**, 237 (1993).
- [6] R.L. Melcher, *Phys. Rev.* **B2**, 733 (1970).
- [7] T.J. Moran, B. Lüthi, *Phys. Rev.* **B4**, 122 (1971).
- [8] K. Sugiyama *et al.*, *J. Phys. Soc. Jpn.* **59**, 3331 (1990).
- [9] B. Wolf *et al.*, *J. Magn. Magn. Mater.* **226–230**, 107 (2001).
- [10] Y. Shapira, *J. Appl. Phys.* **42**, 1588 (1971).
- [11] D. Weber *et al.*, *J. Magn. Magn. Mater.* **76–77**, 315 (1988).
- [12] P. Chandra, P. Coleman, J.A. Mydosh, *Physica B* **312–313**, 397 (2002).