

## MAGNETIC HAMILTONIANS FOR $\text{Li}_2\text{VOSiO}_4$ AND $\text{Li}_2\text{VOGeO}_4$ \*

H. ROSNER, R.R.P. SINGH, W.E. PICKETT

Department of Physics, University of California, Davis, CA 95616, USA

W.H. ZHENG AND J. OITMAA

School of Physics, University of New South Wales, Sydney NSW 2052, Australia

*(Received July 10, 2002)*

Exchange couplings are calculated for the isostructural compounds  $\text{Li}_2\text{VOSiO}_4$  and  $\text{Li}_2\text{VOGeO}_4$  using LDA, suggesting the realization of a large  $J_2/J_1$  quasi-2D spin-half Heisenberg model in both compounds. High temperature expansions for the uniform susceptibility and specific heat are used to fit the experimental data. The range and quality of unbiased fits as a function of the parameters  $J_1$ ,  $J_2$  and  $g$  are reported, confirming  $J_2$  as the largest exchange constant for these materials.

PACS numbers: 71.15.Mb, 75.10.Jm, 75.30.Et

### 1. Introduction

In recent years there has been considerable theoretical interest in the square-lattice Heisenberg model with nearest neighbor (NN) exchange  $J_1$  and second neighbor (NNN) exchange  $J_2$ . However, only very recently the materials  $\text{Li}_2\text{VOSiO}_4$  and  $\text{Li}_2\text{VOGeO}_4$  have been identified [1] as possible realizations of systems with substantial  $J_2/J_1$ . Here, we discuss ab initio calculations for the exchange constants of these materials based on LDA and on fits to the experimental specific heat  $C_P$  and uniform susceptibility  $\chi$  data using high temperature expansions (HTE). The range and quality of unbiased fits are reported as a function of  $J_1$  and  $J_2$ . Both the ab initio calculations and the fits to the experimental data confirm a large  $J_2/J_1$  ratio.

### 2. Electronic structure calculations

$\text{Li}_2\text{VOSiO}_4$  ( $\text{Li}_2\text{VOGeO}_4$ ) crystallizes in the tetragonal system  $P4/nmm$ , with  $a = 6.3682$  (6.4779) Å and  $c = 4.449$  (4.520) Å [2] exhibiting a layered magnetically active network of spin half  $\text{V}^{4+}$  ions. The  $\text{V}^{4+}$  arrangement suggests that both the NN and the NNN in-plane coupling should be significant.

---

\* Presented at the International Conference on Strongly Correlated Electron Systems, (SCES 02), Cracow, Poland, July 10–13, 2002.

In order to obtain a reliable hopping part of a tight-binding (TB) Hamiltonian, band structure calculations were performed using the scalar relativistic full-potential nonorthogonal local-orbital minimum-basis scheme [3] within the LDA.  $V(3s, 3p, 4s, 4p, 3d)$ ,  $O(2s, 2p, 3d)$ ,  $Li(2s, 2p)$ ,  $Si(3s, 3p, 3d)$  and  $Ge(3d, 4s, 4p, 4d)$  states, respectively, were chosen as the basis set. All lower lying states were treated as core states. The paramagnetic calculations result in a valence band complex of about 10 eV width with two bands crossing the Fermi level  $E_F$  (see Fig. 2 in Ref. [4]) and are very similar for both compounds. The two half-filled bands at  $E_F$  originate from the two V per cell and are well separated by a gap of about 3 eV from the rest of the valence band complex. They exhibit mainly V  $3d_{xy}$  and minor O(2)  $2p_{x,y}$  character (oxygens of the basal plane of the  $VO_5$  pyramid). Therefore, strong correlation effects can be expected which explain the experimentally observed insulating ground state.

Because the low-lying magnetic excitations involve only orbitals with unpaired spins corresponding to the half-filled bands, we restrict ourselves to a two band TB analysis taking into account NN transfer  $t_1$  and NNN transfer  $t_2$  within the [001] plane and NN hopping  $t_\perp$  between neighboring planes. Our TB results are shown in the Table. The transfer integrals enable us to estimate the relevant exchange couplings. In the strongly correlated limit, valid for typical vanadates, the superexchange can be calculated in terms of the one-band extended Hubbard model  $J_i^{\text{AFM}} = 4t_i^2/(U_{\text{eff}})$ . From LDA-DMFT(QMC) studies [5] and by fitting spectroscopic data to model calculations [6],  $U_{\text{eff}} \sim 4\text{--}5$  eV is estimated for typical vanadates. Therefore, we adopt  $U_{\text{eff}}=4$  eV and  $U_{\text{eff}}=5$  eV as representative values to estimate the exchange constants and their ranges. Our results are given in the Table.

TB parameters and exchange couplings for  $Li_2VOSiO_4$  ( $Li_2VOGeO_4$ ).

$t_1$ (meV)	$t_2$ (meV)	$t_\perp$ (meV)	$U$ (eV)	$J_1$ (K)	$J_2$ (K)	$J_\perp$ (K)
8.5 (12.8)	29.1 (28.0)	-4.8 (-4.1)	4	0.83 (1.88)	9.81 (9.07)	0.27 (0.20)
			5	0.67 (1.52)	7.85 (7.26)	0.22 (0.16)

Comparing our  $J$ 's with the experimental findings for  $Li_2VOSiO_4$  ( $J_1 + J_2 = 8.2 \pm 1$  K [1]), we find excellent agreement for the sum  $J_1 + J_2 = 9.5 \pm 1.5$  K of the in-plane couplings. In sharp contrast to Ref. [1] where they estimate  $J_2/J_1 \sim 1.1 \pm 0.1$ , we find a ratio  $J_2/J_1 \sim 12$ . In  $Li_2VOGeO_4$  we find a considerable smaller ratio  $J_2/J_1 \sim 5$ .

### 3. Fitting the experimental data

We have developed HTE for  $\chi$  and  $C_P$  of the square-lattice Heisenberg model for arbitrary values of  $J_2/J_1$  [4]. We have previously shown that the LDA-derived exchange constants provide a good description of the experi-

mental properties of these materials [4]. Here, we provide unbiased fits to the experimental data as a function of the exchange constants  $J_1$  and  $J_2$  and the electron's  $g$ -factor in the material.

To judge the quality of the fit, we define [7]

$$P = \text{const.} \sum_{T_i} |A^{\text{exp}}(T_i) - A^{\text{theo}}(T_i)|, \quad (1)$$

where  $A$  can be  $\chi$  or  $C_P$ . The constant in front is irrelevant and is adjusted to scale the plot for presentation. The variation in  $P$  with the model parameters is significant and the smallest  $P$  gives the best fit.

Figures 1 and 2 show the fits for the materials  $\text{Li}_2\text{VOSiO}_4$  and  $\text{Li}_2\text{VOGeO}_4$ , respectively. We see that for  $\text{Li}_2\text{VOSiO}_4$  the best fit from  $C_P$  is very close to  $J_1/J_2 = 0$ . The best fit parameters are  $J_1/J_2 = 0.025$  and  $J_2 = 5.87$  K. The shaded region gives a range of  $J_2$  values for a given  $J_1/J_2$ . The  $\chi$  data give the best fit for  $J_1/J_2 = 0.45$ ,  $J_2 = 5.85$  and  $g = 1.97$ . The fits have been shown in earlier publications [4]. They remain very good even when  $P$  is not at its minimum. The fits get substantially worse and  $P$  begins to increase rapidly only when  $J_1/J_2$  approaches and exceeds unity.

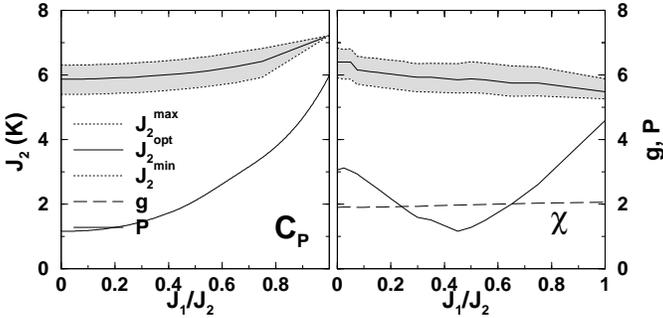


Fig. 1. Best fit parameter ( $J_2$ ,  $J_1/J_2$ ,  $g$ ) for the compound  $\text{Li}_2\text{VOSiO}_4$  from  $C_P$  (left) and  $\chi$  (right).  $P$  gives the quality of the fit (see Eq. (1)).

For the material  $\text{Li}_2\text{VOGeO}_4$  the best fits are obtained from  $C_P$  with parameters  $J_1/J_2 = 0.75$  and  $J_2 = 4.14$ , whereas the best fits for  $\chi$  are with parameters  $J_1/J_2 = 0.55$ ,  $J_2 = 3.84$  and  $g = 1.83$ . Once again, we see that the fits get substantially worse only when  $J_1/J_2$  approaches and exceeds unity.

These fits provide strong support for  $J_2$  being the largest exchange interaction in these materials. The comparison between the two materials shows that  $J_2$  is smaller for  $\text{Li}_2\text{VOGeO}_4$  whereas the  $J_1/J_2$  ratio is somewhat larger in  $\text{Li}_2\text{VOGeO}_4$ . These results are consistent with the LDA calculations. On the whole, thermodynamic quantities are not very sensitive to the  $J_1/J_2$  ratio and an accurate determination of these quantities may come from measurements of spin-wave spectra [4].

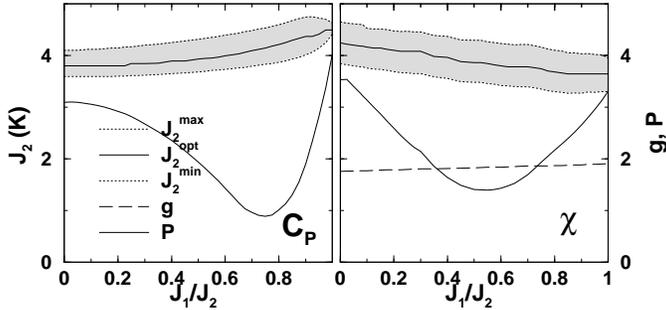


Fig. 2. The same as in Fig. 1 for  $\text{Li}_2\text{VOGeO}_4$ .

#### 4. Conclusions

We have presented first principles calculations for the exchange constants of the materials  $\text{Li}_2\text{VOSiO}_4$  and  $\text{Li}_2\text{VOGeO}_4$ . By comparing HTE fits for  $\chi$  and  $C_P$  with the experimental data we have shown that these materials are in the large  $J_2/J_1$  regime. Because of the demonstrated weak sensitivity of the HTE fits to the assigned parameters, we have also noted that an accurate determination of the  $J_1/J_2$  ratio for such materials could come from the measurement of spin-wave dispersion [4].

We thank F. Mila, O.A. Starykh, S.L. Drechsler and P. Carretta for discussions. This work was supported by the DAAD (H.R.), the NSF DMR-0114818 and DMR-9986948, and by the Australian Research Council.

#### REFERENCES

- [1] R. Melzi, S. Aldrovandi, F. Tedoldi, P. Carretta, P. Millet, F. Mila, *Phys. Rev.* **B64**, 024409 (2001); R. Melzi, P. Carretta, A. Lascialfari, M. Mambrini, M. Troyer, P. Millet, F. Mila, *Phys. Rev. Lett.* **85**, 1318 (2000).
- [2] P. Millet, C. Satto, *Materials Res. Bull.* **33**, 1339 (1998).
- [3] K. Koepf, H. Eschrig, *Phys. Rev.* **B59**, 1743 (1999).
- [4] H. Rosner, R.R.P. Singh, W.H. Zheng, J. Oitmaa, S.-L. Drechsler, W.E. Pickett, *Phys. Rev. Lett.* **88**, 186405 (2002).
- [5] K. Held, G. Keller, V. Eyert, D. Vollhardt, V.I. Anisimov, *Phys. Rev. Lett.* **86**, 5345 (2001).
- [6] A.T. Mizokawa, A. Fujimori, *Phys. Rev.* **B48**, 14150 (1993); J. Zaanen, G.A. Sawatzky, *J. Solid State Chem.* **88**, 8 (1990).
- [7] Z. Weihong, C.J. Hamer, J. Oitmaa, *Phys. Rev.* **B60**, 6608 (1999).