

MAGNETIC PROPERTIES OF CeRhIn₅ UNDER PRESSURE PROBED BY ¹¹⁵In-NQR*

S. KAWASAKI^a, T. MITO^b, G.-Q. ZHENG^a, Y. KAWASAKI^a,
Y. KITAOKA^a, D. AOKI^c, Y. HAGA^d, Y. ŌNUKI^{d,e}

^aDepartment of Physical Science, Graduate School of Engineering Science
Osaka University, Machikaneyama-cho, 1-3 Toyonaka, Osaka 560-8531, Japan

^bFaculty of Science, Kobe University, Kobe, Hyogo 657-8501, Japan

^cDépartement de Recherche Fondamentale sur la Matière Condensée, SPSMS
CEA Grenoble, 38054 Grenoble Cedex 9, France

^dAdvanced Science Research Center, Japan Atomic Energy Research Institute
Tokai, Ibaraki 319-1195, Japan

^eDepartment of Physics, Graduate School of Science, Osaka University
Machikaneyama-cho, 1-3 Toyonaka, Osaka 560-0043, Japan

(Received July 10, 2002)

We report the pressure (P)- induced evolution of the antiferromagnetism in CeRhIn₅ which undergoes a superconducting transition at $T_c \sim 2.1$ K at pressures exceeding $P_c \sim 1.6$ GPa. From measurements of ¹¹⁵In nuclear-spin-lattice-relaxation time (T_1) under P , we found that Néel temperature T_N is reduced above $P = 1.23$ GPa, which is accompanied by an emergent *pseudogap* behavior.

PACS numbers: 74.25.Ha, 74.62.Fj, 74.70.Tx, 75.30.Kz

1. Introduction

Since the discovery of cerium (Ce) based heavy-fermion (HF) superconductivity in CeCu₂Si₂ [1], many experimental works on CeCu₂Ge₂, [2] CeIn₃ [3–5] and CePd₂Si₂ [6] have suggested that antiferromagnetism and superconductivity are closely related each other. The discovery of pressure (P)-induced HF superconductivity in Ce-based antiferromagnetic (AF) compounds has stimulated further experimental works under P [7–10].

A HF AF CeRhIn₅ undergoes a P induced superconducting (SC) transition at a lower critical $P \sim 1.6$ GPa, yet reaching a $T_c \sim 2$ K [7] higher than previous examples. Systematic studies on CeRhIn₅ seem to allow us

* Presented at the International Conference on Strongly Correlated Electron Systems, (SCES 02), Cracow, Poland, July 10–13, 2002.

to unravel an interplay between antiferromagnetism and superconductivity under P . CeRhIn₅ forms in the tetragonal HoCoGa₅ structure that is composed of alternating layers of CeIn₃ and RhIn₂ stacked sequentially along the [001] direction [7]. It orders antiferromagnetically with an incommensurate wave vector $(1/2, 1/2, 0.297)$ [11]. The Néel temperature $T_N = 3.8$ K at $P = 0$ slightly increases up to $P \sim 1.0$ GPa, followed by an onset of superconductivity at $T_c = 2.1$ K at pressures exceeding a critical pressure $P_c \sim 1.63$ GPa [7]. In the previous paper [10], the ¹¹⁵In-NQR study of CeRhIn₅ has clarified the P -induced anomalous magnetism and unconventional superconductivity. In the AF region, T_N which is evidenced from clear shift and splits of NQR spectrum exhibits a moderate increase up to $P = 1.0$ GPa, but decreases above $P = 1.23$ GPa. By contrast, the internal field H_{int} at the In(1) site, that is associated with the magnetic ordering, is almost linearly reduced against increasing P . Note that the In(1) site is equivalent to the In site in the CeIn₃. In the SC region at $P = 2.1$ GPa, it was reported that the $1/T_1$ reveals a T^3 dependence without the coherence peak just below T_c , consistent with the existence of line-node gap [10]. It is, however, not yet clear in CeRhIn₅ how antiferromagnetism evolves into superconductivity with increasing P . Here, we focus on magnetic properties of CeRhIn₅ near $P_c \sim 1.6$ GPa probed by ¹¹⁵In-NQR T_1 measurements in $P = 0 - 1.6$ GPa.

2. Experimental result

The ¹¹⁵In ($I = 9/2$)-NQR spectrum at the paramagnetic state consists of four transitions that are equally spaced with a quadrupole frequency $n \times \nu_Q$ with $n = 1, 2, 3$ and 4. $1/T_1$ was measured at the transitions of $2 \nu_Q$ ($\pm 3/2 \leftrightarrow \pm 5/2$) and $3 \nu_Q$ ($\pm 5/2 \leftrightarrow \pm 7/2$) at the In(1) site, using the conventional saturation-recovery method in the $T = 1, 4 - 100$ K at $P = 0.46, 1.23,$ and 1.6 GPa. Hydrostatic pressure was applied by utilizing a BeCu piston-cylinder cell, filled with Daphne oil (7373) as a pressure-transmitting medium. To calibrate a value of pressure at low temperatures, the shift in T_c of Sn metal under P was monitored by resistivity measurement.

The T dependence of $1/T_1 T$ below 10 K is shown in Fig. 1 at $P = 0.46, 1.23,$ and 1.6 GPa. At the respective values of P , it is clearly seen that AF order occurs at $T_N = 4.0, 3.6$ and 2.8 K, as evidenced by the clear peak in $1/T_1 T$ due to critical magnetic fluctuations toward the AF ordering. This indicates that T_N reduces above $P = 1.23$ GPa as P approaches $P_c \sim 1.63$ GPa. At $P = 1.23$ and 1.6 GPa, $1/T_1 T$ shows a broad peak around T_{PG} well above T_N . This resembles the pseudogap behavior found in high- T_c copper oxide superconductors [12]. Likewise, when P approaches the critical pressures P_c , the low-energy spectral weight of magnetic fluctuations is sup-

pressed before an ordering occurs. We note that the pseudogap behavior has been found in either two- or lower-dimensional strongly correlated electron systems [12]. Very recently, in CeRhIn_5 , anisotropic three dimensional AF fluctuation was reported from neutron scattering at $P = 0$ with an energy scale of less than 1.7 meV at temperatures as high as $3 T_c$ [13]. On the other hand, as P further increases up to $P = 2.1$ GPa where the SC transition appears, $1/T_1 T$ continues to increase down to $T_c = 2.2$ K without any signature for the pseudogap behavior as seen in the previous report [10]. The T variation of $1/T_1 T$ is consistent with the three dimensional AF Fermi-liquid model described by the self-consistent renormalized (SCR) theory for nearly AF metals [10, 14]. Thus the P -induced evolution in the magnetic fluctuations, from a magnetic regime of reduced dimensionality to a more isotropic one, may take place in a narrow P window of 1.6–2.1 GPa, when the AF order evolves into the SC one. The pressure-temperature phase diagram for CeRhIn_5 is summarized in Fig. 2.

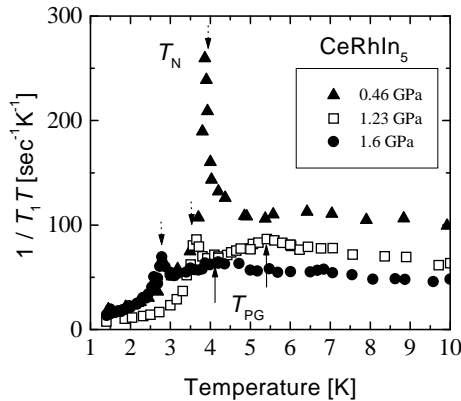


Fig. 1. T dependence of $1 / T_1$ at $P = 0.46, 1.23$ and 1.6 GPa. The solid and dotted arrows indicate T_{PG} and T_N .

In conclusion, we have reported the P -induced evolution of the magnetic properties in CeRhIn_5 on the basis of the ^{115}In -NQR T_1 measurements. In the itinerant antiferromagnet CeRhIn_5 at $P = 0$, T_N slightly increases up to $P = 1.0$ GPa, but it turns to decrease at $P = 1.23$ GPa when approaching $P_c \sim 1.63$ GPa at which superconductivity sets in. This reduction in T_N coincides with the emergence of the pseudogap behavior that is evidenced by the suppression in $1/T_1 T$ above T_N . This P -induced evolution in the magnetic fluctuations, from a magnetic regime of reduced dimensionality to a more isotropic one, may take place in a narrow P window of 1.6–2.1 GPa when the AF order evolves into the SC one.

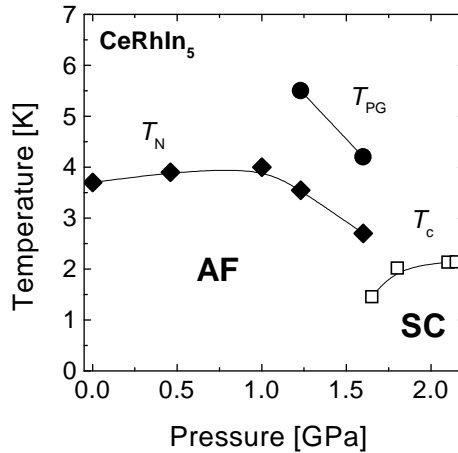


Fig. 2. P - T phase diagram for CeRhIn₅. The open marks are determined from ac-susceptibility measurement [10].

This work was supported by the COE Research (10CE2004) of Grant-in-Aid for Scientific Research from the Ministry of Education, Sport, Science and Culture of Japan. Y. Kawasaki has been supported by JSPS Research Fellowships for Young Scientists.

REFERENCES

- [1] F. Steglich, *et al.*, *Phys. Rev. Lett.* **43**, 1892 (1979).
- [2] D. Jaccard, *et al.*, *Phys. Lett.* **A163**, 475 (1992).
- [3] N.D. Mathur, *et al.*, *Nature* **394**, 39 (1998).
- [4] T. Muramatsu *et al.*, Ph. D. Thesis, Osaka University (2001), unpublished.
- [5] G. Knebel, *et al.*, *Phys. Rev.* **B65**, 024425 (2002).
- [6] F.M. Grosche, *et al.*, *Physica B* **223-224**, 50 (1996); J. Flouquet *et al.*, unpublished.
- [7] H. Hegger, *et al.*, *Phys. Rev. Lett.* **84**, 4986 (2000).
- [8] P. Gegenwart, *et al.*, *Phys. Rev. Lett.* **81**, 1501 (1998).
- [9] Y. Kawasaki, *et al.*, *Phys. Rev.* **B63**, R140501 (2001).
- [10] T. Mito, *et al.*, *Phys. Rev.* **B63**, 220507(R) (2001).
- [11] Wei Bao, *et al.*, *Phys. Rev.* **B62**, R14 621 (2000).
- [12] For review see, T. Timusk, B. Statt, *Rep. Prog. Phys.* **62**, 61 (1999).
- [13] Wei Bao, *et al.*, *Phys. Rev.* **B65**, 100505 (2002).
- [14] T. Moriya, T. Takimoto, *J. Phys. Soc. Jpn.* **64**, 960 (1995).